arXiv:0908.3557v1 [cond-mat.str-el] 25 Aug 2009

Low temperature properties of the Electron Spin Resonance in YbRh$_2$Si$_2$

J. Sichelschmidt*,1, T. Kambe2, I. Fazlishanov3, D. Zakharov4, H.-A. Krug von Nidda4, J. Wykhoff1, A. Skvortsova5, S. Belov5, A. Kutuzov5, B.I. Kochelaev5, V. Pashchenko 6, M. Lang 6, C. Krellner1, C. Geibel1, F. Steglich1

[1] Max Planck Institute of Chemical Physics of Solids, 01187 Dresden, Germany
[2] Okayama University, Department of Physics, Okayama 700-8530, Japan
[3] E.K. Zavoisky Physical-Technical Insitute, 420049 Kazan, Russia
[4] Experimental Physics V, Center for Electronic Correlations and Magnetism, University of Augsburg, 86159 Augsburg, Germany
[5] Theoretical Physics Departement, Kazan State University, 420008 Kazan, Russia
[6] Physikalisches Institut, Goethe-Universität Frankfurt, 60438 Frankfurt(M), Germany

Received XXXX, revised XXXX, accepted XXXX
Published online XXXX

PACS 76.30.Kg, 71.27.+a

---

* Corresponding author: e-mail Sichelschmidt@cpfs.mpg.de, Phone: +49-351-46463221, Fax: +49-351-46463232

We present the field and temperature behavior of the narrow Electron Spin Resonance (ESR) response in YbRh$_2$Si$_2$ well below the single ion Kondo temperature. The ESR g- factor reflects a Kondo-like field and temperature evolution of the Yb^{3+} magnetism. Measurements towards low temperatures (> 0.6K) have shown distinct crossover anomalies of the ESR parameters upon approaching the regime of a well defined heavy Fermi liquid. Comparison with the field dependence of specific heat and electrical resistivity reveal that the ESR parameters can be related to quasiparticle mass and cross section and, hence, contain inherent heavy electron properties.

1 Introduction The heavy fermion metal YbRh$_2$Si$_2$ has proven to display a variety of unusual low temperature electronic properties which are related to the interplay between the Kondo interaction of Yb^{3+} $4f$ spin / conduction electron spin and the indirect magnetic RKKY interaction of the $4f$ spins. It is located very close to a magnetic instability where a weak antiferromagnetic long range order below 70 mK is suppressed by a magnetic field of $B_c = 60$ mT. In the vicinity of such a magnetic field induced quantum critical point and at low temperature (T) pronounced non-Fermi liquid behavior is observed as evidenced by a divergence of the electronic specic heat and electrical resistivity $\rho \propto T$. At higher fields electronic specific heat C, magnetic susceptibility, and ρ show Landau-Fermi liquid (LFL) behavior with a renormalized electronic mass and quasiparticle scattering [1]. YbRh$_2$Si$_2$ is one of a few Kondo lattice compounds where a well-defined Electron Spin Resonance (ESR) signal allows to directly characterize the spin dynamics of the Kondo ion. Even well below a thermodynamically defined single ion Kondo temperature ($T_\mathrm{K} \simeq 20$ K) this signal shows properties typical for localized $4f$ moments[2,3]. It has been shown that the presence of strong ferromagnetic correlations between the $4f$-spins enables an ESR signal narrow enough to be observed [4]. Here we investigate the properties of this signal at low temperatures and as a function of low fields, below and above B_c.

2 Experiment We present results of ESR measurements with standard continuous wave techniques at four microwave frequencies ($\nu = 1.1, 9.4, 34, 56$ GHz) which according to the resonance condition $h\nu = g\mu_\mathrm{B} B_\mathrm{res}$ correspond to the resonance fields $B_\mathrm{res} = 0.02, 0.19, 0.68, 1.1$ T providing the field dependence of the ESR parameters. The sample was cooled by a ^{4}He flow cryostat ($T > 3$ K), a ^{4}He bath cryostat ($4 > T > 1.5$ K), and a ^{3}He bath cryostat ($2 > T > 0.6$ K) [5]. As was shown previously [6] samples with different resistivity ratios

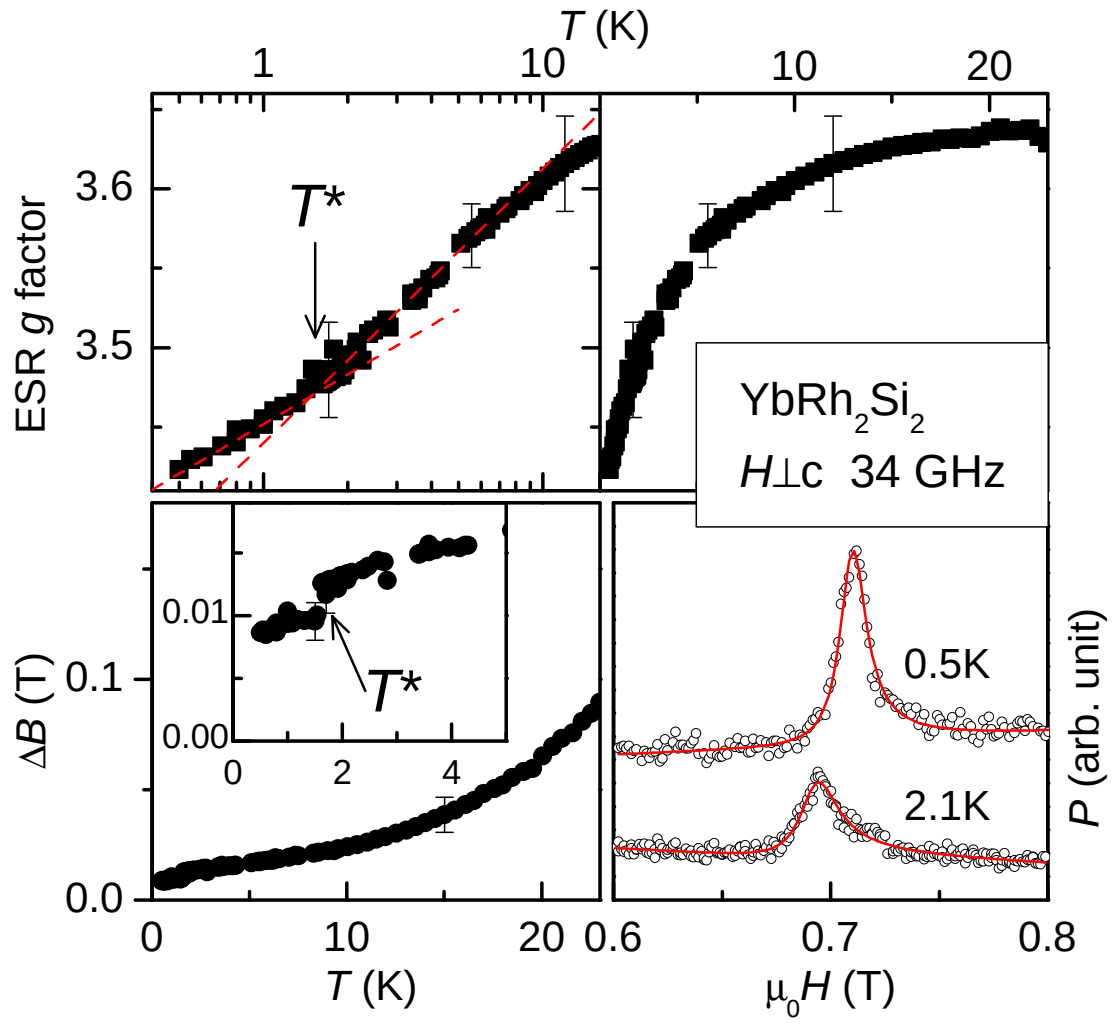

Figure 1 Low temperature behavior of the Q-band (34 GHz) ESR parameters linewidth (ΔB) and g factor (dashed lines: $g \propto \ln T$). T^* indicates the temperature of the crossover into a heavy Landau Fermi Liquid state, see the $B - T$ phase-diagram in [1]. Lower right panel shows ESR spectra (P: absorbed microwave power) at indicated temperatures fitted by Lorentzian lineshapes (solid lines).

(RR $\equiv \rho(300\mathrm{K})/\rho(1.8\mathrm{K})$) show differences in their ESR response and, therefore, we used the same single crystal of $YbRh_2Si_2$ with RR=20. We ensured a proper crystal alignment (external field H within tetragonal a,b-plane; $H \perp$ c) by minimizing the highly anisotropic resonance field. All spectra could be nicely fitted with a single Lorentzian line (containing dispersive contributions due to a finite penetration depth [7]) as shown in the inserted frame of Fig.1.

3 Results The transport and magnetic properties of $YbRh_2Si_2$ are considerably affected below T_K by external magnetic fields up to 10 T [1], reflecting the strong interaction of the conduction electron spins with the Yb^{3+} $4f$ electrons which determine the magnetism with pronounced local properties [8]. Below a characteristic temperature T^* the Sommerfeld coefficient of the specific heat and the magnetic susceptibility approach Landau Fermi liquid behavior. Fig. 1 displays the behavior of the ESR response above and below T^*: Above T^* the ESR g-factor logarithmically increases, reflecting the Kondo interaction between $4f$ and conduction electrons [2] (see below for the other Kondo-like features of g). As shown by the dashed lines in Fig. 2b the linewidth shows a Korringa-like increase linear in temperature followed by an exponential increase due to spin-phonon interaction caused by crystal field modulations via lattice vibrations [6]. When crossing T^* from above the slope of the logarithmic g-factor decreases and the linewidth shows a step-like decrease. Similar, but less pronounced behavior has also been found for higher frequencies (i.e. higher magnetic fields) [9].
The temperature behavior of both g factor and linewidth strongly depend on the magnetic field. Fig.2 shows this dependence that we measured by using four microwave excitation frequencies corresponding to four resonance magnetic fields. The ESR g factor offers a characteristic Kondo-like behavior, namely a weakening of the logarithmic temperature dependence when the magnetic field is increased, further confirming the finding of Ref. [9] with two additional frequencies 1.1GHz and 56 GHz, respectively. At all investigated fields and for $T \lesssim 10$ K the linewidth shows a linear T dependence, $\Delta B = a + b \cdot T$. The anomaly at T^* (arrow) is found for the 34 GHz / 0.68 T data only. This is because the data at 0.02 T and 0.19 T are taken at $T > T^*$ and at 1.1 T the data accuracy is insufficient to resolve the anomaly at T^*. At low fields the slope b varies slightly but not monotonous with field, see Fig.2c. Note in particular the slope of the 0.68 T data which is smaller than the slope of the 0.19 T data. The residual linewidth a and, to a lesser extend, the slope b roughly vary with B^2 as indicated by the dashed line. Although $a \propto B^2$ points towards an inhomogeneous broadening such behavior would also be consistent with a bottleneck relaxation of the coupled Yb^{3+}- conduction electron resonant collective mode as was identified from ESR investigations of Lu-doped $YbRh_2Si_2$ [10].

4 Discussion The ESR of $YbRh_2Si_2$ clearly reflects the local magnetic properties of the Kondo ion Yb^{3+} and should contain valuable information on the Kondo interaction between $4f$ spins and conduction electrons. A suppression of the Kondo effect by magnetic field and temperature should therefore be visible in the ESR linewidth and in the g-factor. This, indeed, is qualitatively seen in Figs.2(a) and 2(b) and was reported for high field values

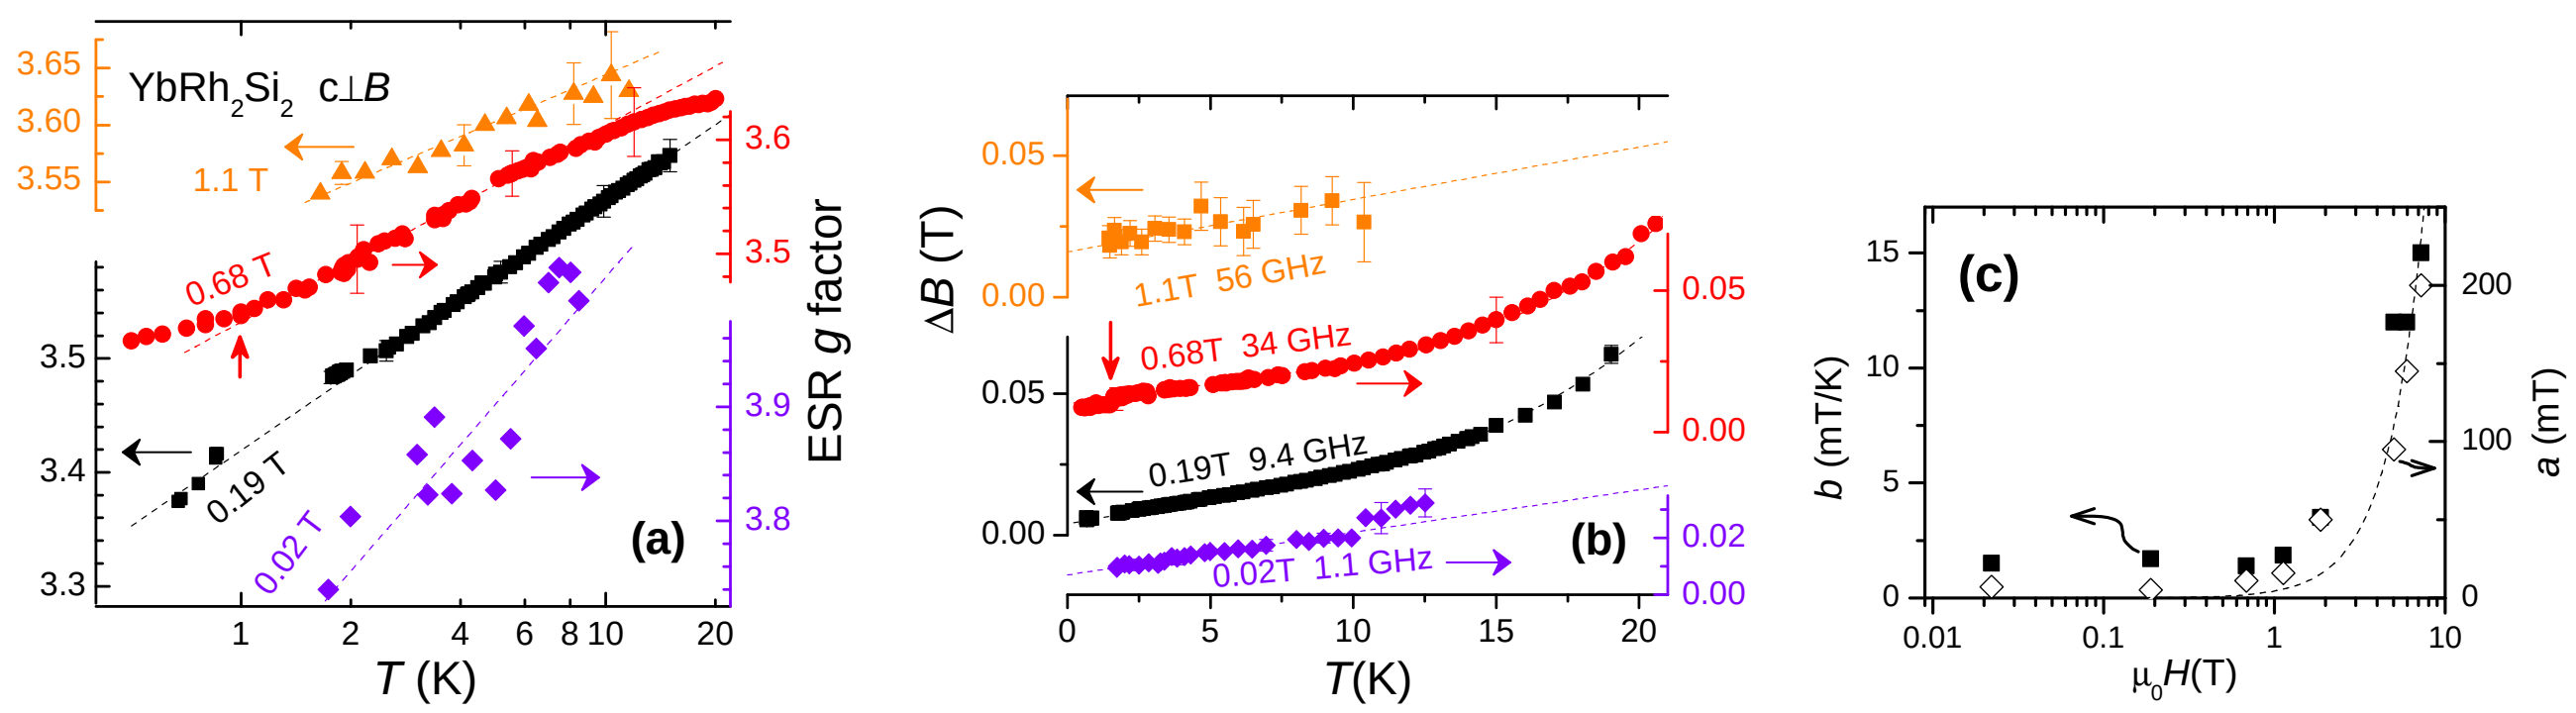

Figure 2 Temperature dependence of (a) the ESR g factor (lines: $g \propto \ln(T)$) and (b) the linewidth ΔB (dashed lines see main text). Data in (a) and (b) are depicted for various microwave frequencies corresponding to resonance fields measured at $T = 5$ K. Vertical arrows indicate T^*, compare Fig.1. Frame (c) displays a, b of $\Delta B = a + b \cdot T$ (linear part of lines in (b), data for $\mu_0 H > 1.8$ T from [9]). Dashed line indicates $a \propto B^2$.

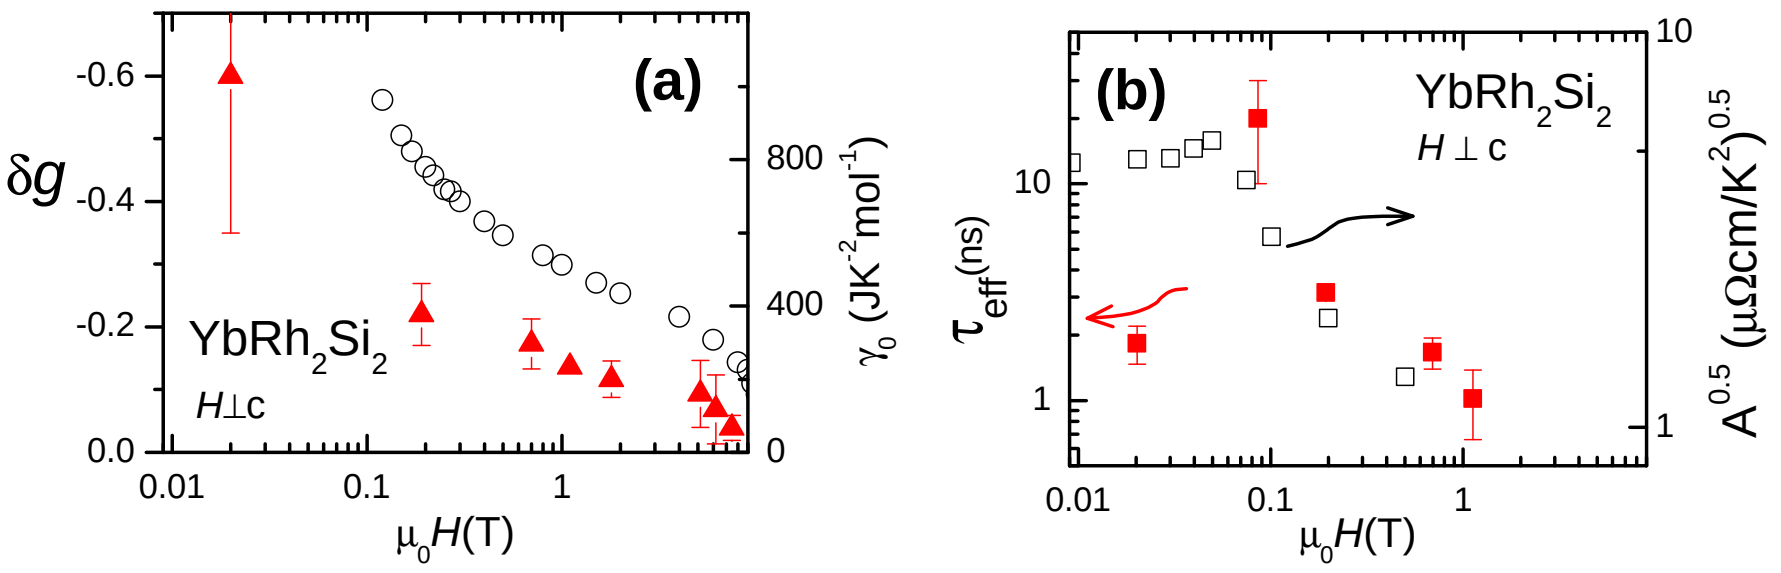

Figure 3 Field dependence of (a) the ESR g factor temperature variation, $\delta g = g(2\,\mathrm{K}) - g(20\,\mathrm{K})$ (data for $\mu_0 H > 1.8$ T from [9]), and (b) the effective relaxation time $\tau_{\mathrm{eff}}(1.8\mathrm{K}) = B_{\mathrm{res}}/(\nu \Delta B)$ (with $\tau_{\mathrm{eff}}(0.086\,\mathrm{T})$ obtained from linear extapolation of ΔB in [10]). Data are compared with the specific heat Sommerfeld coefficient γ_0 [11] and the quasiparticle scattering cross section A [12], respectively.

in Ref.[9]. We quantitatively captured the g-factor behavior of Fig.2a by plotting the difference of the g factor at low and high temperatures, $\delta g = g(2\mathrm{K}) - g(20\mathrm{K})$. This is shown in Fig.3a and confirms the close relation to the Sommerfeld coefficient γ_0 which is a measure of m^*. Note the further increasing δg at fields below the critical field $B_c = 60$ mT, i.e. in a region with a long range, but weak antiferromagnetic ordering which has the signatures of a heavy LFL state according to $\rho(T,B)$ and $C(T,B)$ with $\gamma_0 \simeq 1.7\ \mathrm{JK^{-2}mol^{-1}}$.

Assuming that the observed resonance may be described by a heavy electron spin resonance a semiphenomenological Fermi-liquid description could explain the linewidth narrowing provided by hybridization, i.e. the linewidth ΔB should contain a factor m/m^* (where m is the free electron mass and m^* is the effective quasiparticle mass) [13]. Hence, the effective spin relaxation time $\tau_{\mathrm{eff}} = B_{\mathrm{res}}/(\nu \Delta B)$ should be proportional m^*. Indeed, as shown in Fig.3b, τ_{eff} at $T = 1.8$ K increases with decreasing field, similar to the behavior of $\gamma_0 \propto m^*$ and in agreement with the assertion of a Fermi liquid description [13]. However, this trend does not to seem to be continued for fields below the critical field $B_c = 60$ mT. On the other hand such behavior is reminiscent to the magnetic field dependence of the quasiparticle scattering cross section A that diverges at B_c from both sides [12] and that is proportional to m^{*2}. As shown in Fig.3b a comparison of τ_{eff} with $\sqrt{A}$ again suggests $\tau_{\mathrm{eff}} \propto m^*$. Such proportionality shows that the relaxation between Yb^{3+} spins and heavy conduction electrons does not determine the linewidth because then an increasing m^* would *suppress* τ_{eff} by a Korringa mechanism. This indicates a bottleneck relaxation of a strongly coupled Yb^{3+}- conduction electron resonant collective mode as supported by other experimental results [6, 10]. The realisation of such a collective spin mode in the presence of a strong magnetic anisotropy and Kondo interactions will be described in a forthcoming paper.

5 Conclusion Our low-temperature ESR measurements at 34 GHz (0.68 T) of the Kondo lattice compound YbRh$_2$Si$_2$ confirmed a continuos decrease of the linewidth for temperatures upon cooling down to 0.6 K. Both g-factor and linewidth display a crossover behavior for the same temperatures where thermodynamic and static magnetic properties indicate a crossover to LFL behavior. Compared to ESR results at higher fields [9] the crossover of the ESR parameters at 0.68 T appears more pronounced and in a much narrower temperature range. We confirmed the Kondo-like behavior of the field/temperature dependence of the ESR g factor for fields down to 20 mT, i.e. smaller than the critical field $B_c = 60$ mT. The field dependence of the low-temperature linewidth agrees with the behavior of the quasiparticle cross section.

Acknowledgements We acknowledge support by the Volkswagen foundation (project I/82 203).

References

[1] P. Gegenwart, Q. Si, and F. Steglich, Nature Phys. **4**(3), 186 (2008).

[2] J. Sichelschmidt, V. Ivanshin, J. Ferstl, C. Geibel, and F. Steglich, Phys. Rev. Lett. **91**, 156401 (2003).

[3] J. Sichelschmidt, J. Wykhoff, H. A. K. von Nidda, J. Ferstl, C. Geibel, and F. Steglich, J. Phys. Cond. Mat. **19**(11), 116204 (2007).

[4] C. Krellner, T. Förster, H. Jeevan, C. Geibel, and J. Sichelschmidt, Phys. Rev. Lett. **100**(6), 066401 (2008).

[5] K. Kajiyoshi, T. Kambe, M. Tamura, and K. Oshima, J. Phys. Soc. Jap. **75**, 074702 (2006).

[6] J. Wykhoff, J. Sichelschmidt, J. Ferstl, C. Krellner, C. Geibel, F. Steglich, I. Fazlishanov, and H. A. K. von Nidda, Physica C **460-462**, 686 (2007).

[7] J. Wykhoff, J. Sichelschmidt, G. Lapertot, G. Knebel, J. Flouquet, I. I. Fazlishanov, H. A. Krug von Nidda, C. Krellner, C. Geibel, and F. Steglich, Science Techn. Adv. Mat. **8**(5), 389 (2007).

[8] A. Kutuzov, A. Skvortsova, S. Belov, J. Sichelschmidt, J. Wykhoff, I. Eremin, C. Krellner, C. Geibel, and B. Kochelaev, J. Phys. Cond. Mat. **20**(45), 455208 (2008).

[9] U. Schaufuss, V. Kataev, A. A. Zvyagin, B. Buchner, J. Sichelschmidt, J. Wykhoff, C. Krellner, C. Geibel, and F. Steglich, Phys. Rev. Lett. **102**(7), 076405 (2009).

[10] J. G. S. Duque, E. M. Bittar, C. Adriano, C. Giles, L. M. Holanda, R. Lora-Serrano, P. G. Pagliuso, C. Rettori, C. A. Perez, R. Hu, C. Petrovic, S. Maquilon, Z. Fisk, D. L. Huber, and S. B. Oseroff, Phys. Rev. B **79**(3), 035122 (2009).

[11] N. Oeschler, S. Hartmann, A. Pikul, C. Krellner, C. Geibel, and F. Steglich, Physica B **403**, 1254 (2008).

[12] P. Gegenwart, J. Custers, C. Geibel, K. Neumaier, T. Tayama, K. Tenya, O. Trovarelli, and F. Steglich, Phys. Rev. Lett. **89**, 056402 (2002).

[13] E. Abrahams and P. Wölfle, Phys. Rev. B **78**(10), 104423 (2008).